

# Queo™ 0210

## Octene-1 Plastomer

### DATA SHEET

#### Description and Attributes

Queo™ 0210 is an ethylene based octene plastomer, produced in a solution polymerisation process using a metallocene catalyst.

Queo 0210 is an effective and versatile blend partner for other polyolefin polymers, providing :

- Excellent PP compatibility
- High flexibility
- Outstanding toughness
- Excellent low-temperature flex-cracking resistance
- High clarity

#### Applications

Demonstrated applications include :

- Household consumer goods
- High clarity PP moulded goods
- Closures
- Masterbatch carrier
- Wire and cable compounds
- Highly filled compounds
- Extrusion coated structures

<b>General properties</b>	<b>Units</b>	<b>Typical values [1]</b>	<b>Method</b>
Melt Flow Rate (2.16 kg/190°C)	dg/min	10	ISO 1133
Density (23°C)	kg/m <sup>3</sup>	902	ISO 1183
Shore D hardness	--	38	ISO 868
DSC peak melting point	°C	97	ISO 11357
Vicat softening temperature (at 10 N)	°C	75	ISO 306
Brittleness temperature	°C	< -76	ASTM D746

#### Moulded plaque properties [2]

Tensile strength at break	MPa	14	ISO 527-2 (5A)
Elongation at break	%	930	ISO 527-2 (5A)
Flexural modulus	MPa	65	ISO 178
Notched Izod at 23°C	kJ/m <sup>2</sup>	No break	ISO 180 (1A)
Environmental stress crack resistance	hr	> 1000	ASTM D1693 (method b)


#### Extrusion coating performance of blend with 40 weight % LDPE [3]

Neck-in at 100 m/min	cm	6.8	Internal method
Draw down	m/min	490	Internal method

[1] Values are typical and not to be interpreted as specifications.

[2] Specifics of compression moulded test specimen.

[3] Determined on pilot extrusion coating line with air gap at 170 mm, constant output at 35 rpm and 295 °C.

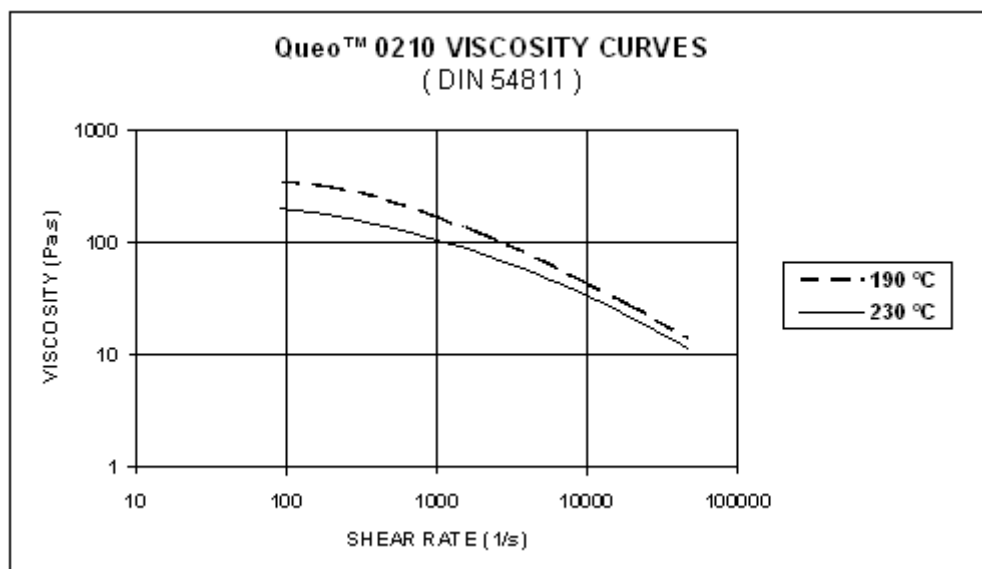

### Additives

Queo 0210 contains processing stabilizers.

### Food Law Compliance and Product Handling

Queo 0210 can - in principle - be used in food contact applications in various EU Member States and in the USA (FDA). Migration or use limitations may apply. Please contact your sales representative for more detailed information and/or actual compliance certification documents.

Specific information on material safety aspects of Queo 0210 will be provided upon request.

### Standard Packaging

Queo 0210 is supplied as free flowing pellets in bulk or packaged in 25 kg bags. The 25 kg bags are assembled on a heat treated pallet to a net weight of 1'375 kg and covered with a stretch hood.

### Further information

Borealis AG  
Wagramerstrasse 17-19  
1220 Vienna  
Austria  
Telephone +43 1 224 00 0  
Fax +43 1 22 400 333

FN 269858a  
CCC Commercial Court of Vienna

Website [www.borealisgroup.com](http://www.borealisgroup.com)

### Disclaimer

**The product(s) mentioned herein are not intended to be used for medical, pharmaceutical or healthcare applications and we do not support their use for such applications.**

To the best of our knowledge, the information contained herein is accurate and reliable as of the date of publication, however we do not assume any liability whatsoever for the accuracy and completeness of such information.

**Borealis makes no warranties which extend beyond the description contained herein. Nothing herein shall constitute any warranty of merchantability or fitness for a particular purpose.**

**It is the customer's responsibility to inspect and test our products in order to satisfy itself as to the suitability of the products for the customer's particular purpose. The customer is responsible for the appropriate, safe and legal use, processing and handling of our products.**

No liability can be accepted in respect of the use of Borealis' products in conjunction with other materials. The information contained herein relates exclusively to our products when not used in conjunction with any third party materials.

Queo™ is a trademark of the Borealis Group.